arXiv:1107.1433v1 [cond-mat.str-el] 7 Jul 2011

Evidence for a pressure-induced quantum liquid in $KCuF_3$

S. Yuan,[1] M. Kim,[1] J. Seeley,[1] S. Lal,[1,2] P. Abbamonte,[1] and S.L. Cooper[1]
[1] *Department of Physics and Frederick Seitz Materials Research Laboratory,*
University of Illinois, Urbana, Illinois 61801, USA
[2] *Department of Physical Sciences, IISER-Kolkata,*
Mohanpur campus, West Bengal - 741252, India

(Dated: July 8, 2011)

Pressure-dependent, low temperature inelastic light (Raman) scattering measurements of $KCuF_3$ show that applied pressure above $P^* \sim 7$ kbar reverses a previously observed low temperature structural distortion in $KCuF_3$, resulting in the development of a $\omega \sim 0$ fluctuational (quasielastic) response near $T \sim 0$ K. This pressure-induced fluctuational "central peak" — associated with slow fluctuations of the CuF_6 octahedral orientation — is temperature independent and exhibits a characteristic fluctuation rate that is much larger than the temperature, $\Gamma \gg k_B T$, consistent with quantum fluctuations of the CuF_6 octahedra. A model of pseudospin-phonon coupling — where the pseudospin represents different configurations of the CuF_6 octahedral tilts — nicely describes both the temperature- and pressure-dependent evolution of the Raman spectra of $KCuF_3$.

PACS numbers: 78.30.-j, 62.50.-p, 75.25.Dk

Frustrated magnetic systems in which conventional static order is suppressed down to $T = 0$ K are currently of great interest because of the possibility that these systems exhibit underlying order, e.g., off-diagonal long range order,[1] and novel "liquid-like" ground states — such as orbital [2] and spin liquids [3] — which quantum mechanically fluctuate even at $T = 0$ K. Unfortunately, there are only a few examples of materials in which such orbital/spin liquid ground states have been reported.[2,3]

In this paper, we report evidence for a pressure-tuned quantum melting transition in $KCuF_3$ between a static structural phase to a phase in which the structure dynamically fluctuates even at $T \sim 0$ K. While often considered a model system for orbital-ordering behavior,[4] the $3d^9$ perovskite $KCuF_3$ has long been known to exhibit a number of unusual properties that are still not well understood, including a highly anisotropic exchange coupling ($J_c/J_a \sim -100$) [5] that results in 1D antiferromagnetic Heisenberg spin dynamics above 40 K;[6–8] a large disparity between the orbital ordering temperature ($T_{oo} \sim 800$ K [9]) and the Néel ordering temperature ($T_N \sim 40$ K [5,8]) that cannot be explained by conventional superexchange models;[10] and several structural anomalies suggesting that $KCuF_3$ exhibits orthorhombic domains [11–14] whose dynamical fluctuations are interrupted by a structural distortion to a static configuration at $T \sim 50$ K.[15,16]

Pressure-dependent, low temperature inelastic light (Raman) scattering measurements reported here show that applied pressure above $P^* \sim 7$ kbar reverses the previously observed [16] low temperature structural distortion in $KCuF_3$ down to the lowest temperatures measured ($T = 3$ K), resulting in the development of a fluctuational (quasielastic) response near $T \sim 0$ K. This pressure-induced fluctuational ("central peak") response — which we associate with slow fluctuations of the CuF_6 octahedral orientation — is temperature independent and exhibits a characteristic fluctuation rate that is much larger than the temperature, $\Gamma \gg k_B T$, similar to the behavior observed in "quantum paraelectric" phases such as $SrTiO_3$ and $KNaO_3$.[1] A model of pseudospin-phonon coupling [17] — where the pseudospin represents different configurations of the CuF_6 octahedral tilts — nicely describes both the temperature- and pressure-dependent evolutions of the Raman spectra of $KCuF_3$.

Single crystal samples of $KCuF_3$ were grown by an aqueous solution precipitation method described previously.[18] Samples were characterized with magnetic susceptibility and X-ray diffraction measurements, and the results obtained are in good agreement with previous results.[6,7,19] Low temperature, pressure-dependent Raman scattering measurements — using liquid argon as the quasihydrostatic pressure medium — were performed using the 6471 $\AA$ line from a krypton laser and a SiC- or diamond-anvil cell that fits in a flow-through helium cryostat, allowing simultaneous control of temperature ($T \geq 3$ K) and pressure ($P \leq 100$ kbar).

Fig. 1 summarizes the temperature-dependence ($P = 0$) of some of the key phonon modes in $KCuF_3$,[16,20] showing that the structure of $KCuF_3$ is unstable above $T = 50$ K. In particular, Figs. 1 (a) and (b) show that the B_{1g}-symmetry phonon near 72 cm^{-1} exhibits a roughly 10-fold decrease in linewidth (FWHM) and a 20% decrease in energy ("softening") with decreasing temperature (Fig. 1), consistent with previous evidence for thermally driven structural fluctuations that persist over an anomalously broad range of temperature between T_N (=40 K) and 300 K.[11–14,16] Fig. 1 also shows that the B_{1g} phonon frequency stabilizes at temperatures below ~ 50 K, concomitant with a splitting of the doubly degenerate 260 cm$^{-1}E_g$ mode into two singly degenerate modes at 260 cm^{-1} and 265 cm^{-1} (Figs 1 (c) and (d)), providing evidence that the thermally driven structural fluctuations in $KCuF_3$ are arrested by a structural tran-

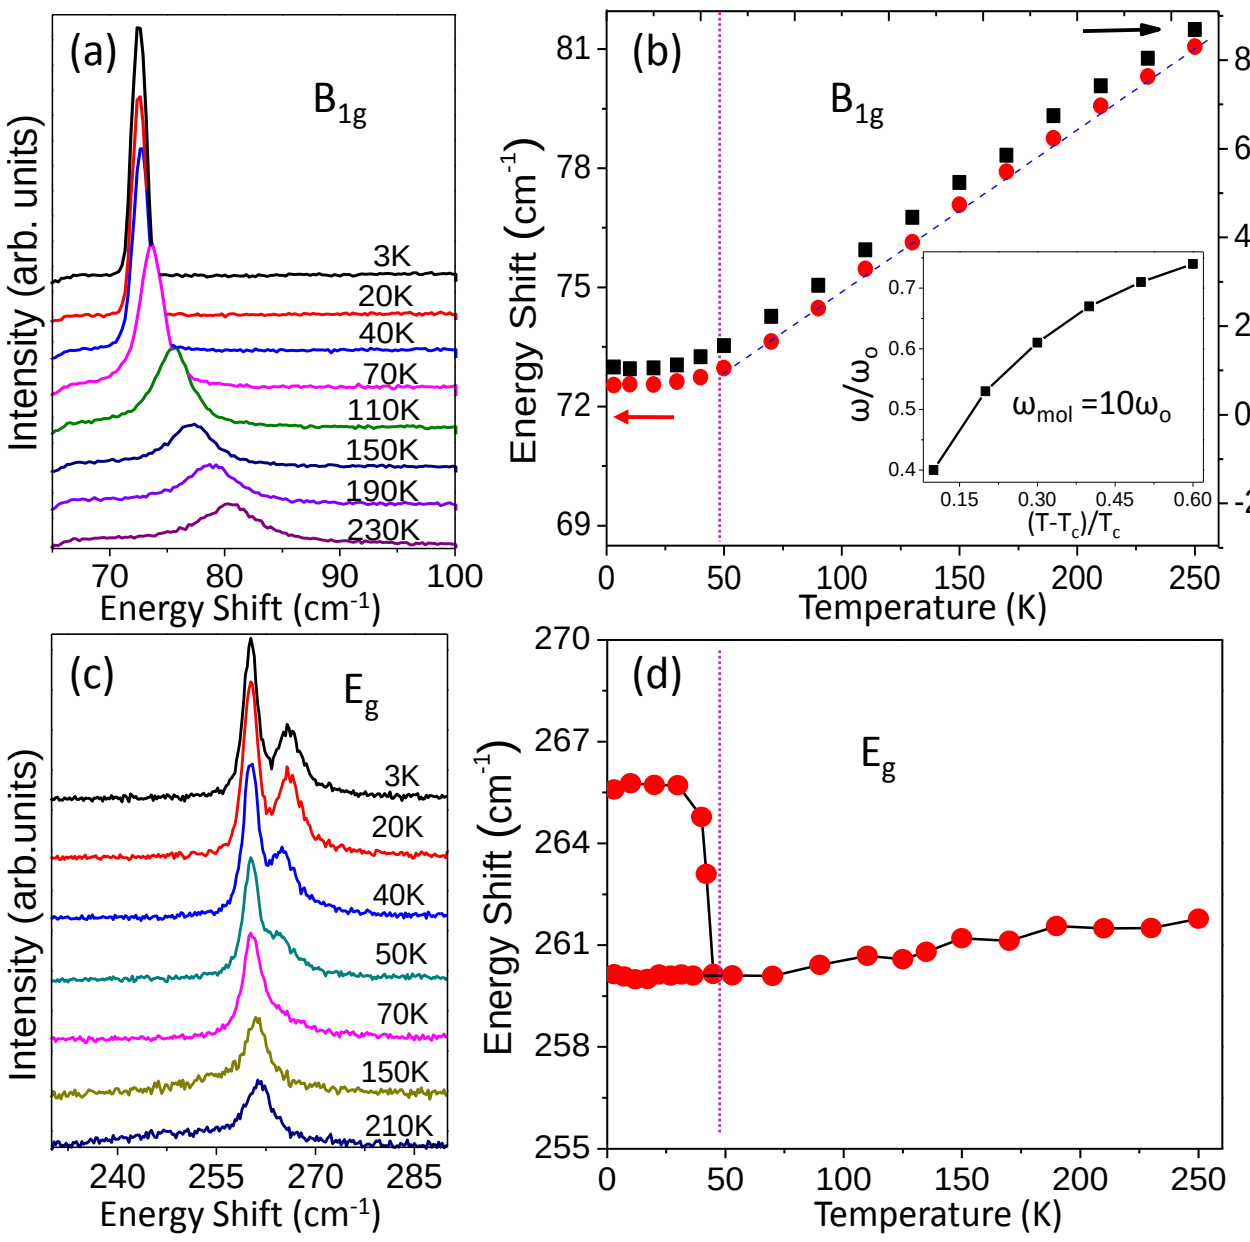

FIG. 1. (a) Temperature dependence of the B_{1g} symmetry phonon mode in $KCuF_3$. (b) Summary of the temperature dependence of the peak energy (circles) and linewidth (squares) of the B_{1g} phonon mode. The inset shows the calculated temperature dependence of the normalized peak frequencies, ω/ω_o, using Eq. 1 for the case $\omega_{mol} = 10\omega_o$, from [17]. (c) Temperature dependence of the E_g symmetry phonon mode in $KCuF_3$. (d) Summary of the temperature dependence of the peak energy of the E_g phonon mode, showing a splitting of the mode at the tetragonal-to-orthorhombic structural transition at $T = 50$ K.

sition.[15,16,20]

It has been previously suggested that anomalies in X-ray diffraction [16] and electron spin resonance [12] measurements of $KCuF_3$ arise from dynamical rotations of the CuF_6 octahedra, which freeze into a static $GdFeO_3$-type pattern at $T \sim 50$ K.[16] In support of this interpretation, the thermally driven mode softening behavior in $KCuF_3$ (Fig. 1) can be well-described by a coupled pseudospin-phonon model [17] in which the atomic vibrations of the phonons are associated with molecular groups (e.g., the CuF_6 octahedra in $KCuF_3$) that fluctuate between discrete configurations and whose dynamics can be described using a pseudospin representation. The associated Hamiltonian is given by,[17]

$$H=\frac{1}{2}\sum_{K}\left\{P\left(k\right)P^{*}\left(k\right)+\omega_o^2(k)Q(k)Q^{*}(k)\right\}$$
$$-\frac{1}{2}\sum_{i,j}J_{ij}\sigma_i\sigma_j+\sum_{k,j}\frac{\omega_0(k)}{\sqrt{N}}g(k)Q(k)\sigma_j e^{ik\cdot r_j}$$

where Q is the normal coordinate of the phonon, P is the conjugate coordinate of Q, σ_i is the pseudospin, J_{ij} is the pair interaction between the ith and jth pseudospins, g is the pseudospin-phonon coupling constant, and ω_o is the bare phonon frequency. The coupled phonon response function associated with this Hamiltonian is:[17]

$$\Phi=\frac{2\gamma k_B T\left(\frac{g}{\gamma J'}\right)^2}{\left[\omega^2-\overline{\omega}_o^2\right]^2+\omega^2\Gamma_1^2} \qquad (1)$$

where $\gamma \sim \omega_{mol}$ is the pseudospin (CuF_6 octahedra) fluctuation rate, $J' = k_B T - J$ is the renormalized exchange coupling, $\overline{\omega}_o \left\{= \omega_o\left[1-\left(g^2/J'\right)\right]^{1/2}\right\}$ is the renormalized phonon frequency, and $\Gamma_1 \left\{= \left(\omega^2-\omega_o^2\right)/\gamma J'\right\}$ is the phonon damping parameter. Notably — as illustrated in the inset of Fig. 1(b) for the case $\omega_{mol} = 10\omega_o$ — when the molecular fluctuation rate (ω_{mol}) is much faster than the phonon frequency (ω_o), i.e., for $\omega_{mol} \gg \omega_o$, the phonon response function in Eq. 1 predicts that the coupled phonon will exhibit mode softening as the temperature decreases towards the structural phase transition ($T \rightarrow T_c$).[17] This regime is consistent with the mode softening observed for the 50 cm^{-1} E_g [16] and 72 cm^{-1} B_{1g} rotational F phonon modes in $KCuF_3$ (see Fig. 1(a) and (b)), supporting our conclusion that the anomalous mode softening in $KCuF_3$ is associated with CuF_6 octahedral fluctuations, and revealing a thermally driven fluctuational regime in $KCuF_3$ in which thermal fluctuations of the CuF_6 octahedra occur on a much faster timescale than the E_g and B_{1g} phonon frequencies to which they are coupled.

Significantly, evidence that CuF_6 octahedral fluctuations in $KCuF_3$ extend down to very low temperatures $\sim$ 50 K in $KCuF_3$ — and are interrupted only by a structural distortion that locks these fluctuations into a static ('glassy') configuration [16] — suggests that $KCuF_3$ is close to a quantum critical point (QCP) at which the fluctuational regime extends down to $T = 0$ K. To observe "quantum melting" between $T \sim 0$ static and fluctuational regimes in $KCuF_3$, low-temperature, pressure-dependent Raman scattering measurements were performed on $KCuF_3$. Hydrostatic pressure has been shown to reduce octahedral distortions in perovskite materials such as $(La,Ba)_2CuO_4$,[21] Ca_2RuO_4,[22] $Ca_3Ru_2O_7$,[23] and $LaMnO_3$.[24] Consequently, pressure-tuning offers a means of reversing the low-temperature tetragonal-to-orthorhombic distortion in $KCuF_3$ that accompanies the freezing-in of CuF_6 octahedral rotations below $T = 50$ K (and $P = 0$).

Fig. 2 shows the pressure-dependent Raman spectra of $KCuF_3$. The insets of Fig. 2 (a) and (b) show that the splitting of the ~ 260 cm^{-1} E_g phonon mode disappears above $P^* \sim 7$ kbar, indicating a pressure induced orthorhombic-to-tetragonal distortion. Figures 2 (a) and (b) also show that the pressure-induced structural transition near $P^* \sim 7$ kbar (at $T = 3$ K) is followed by the development with increasing pressure of a quasielastic central peak; this pressure-induced fluctuational response is approximately described by a sim-

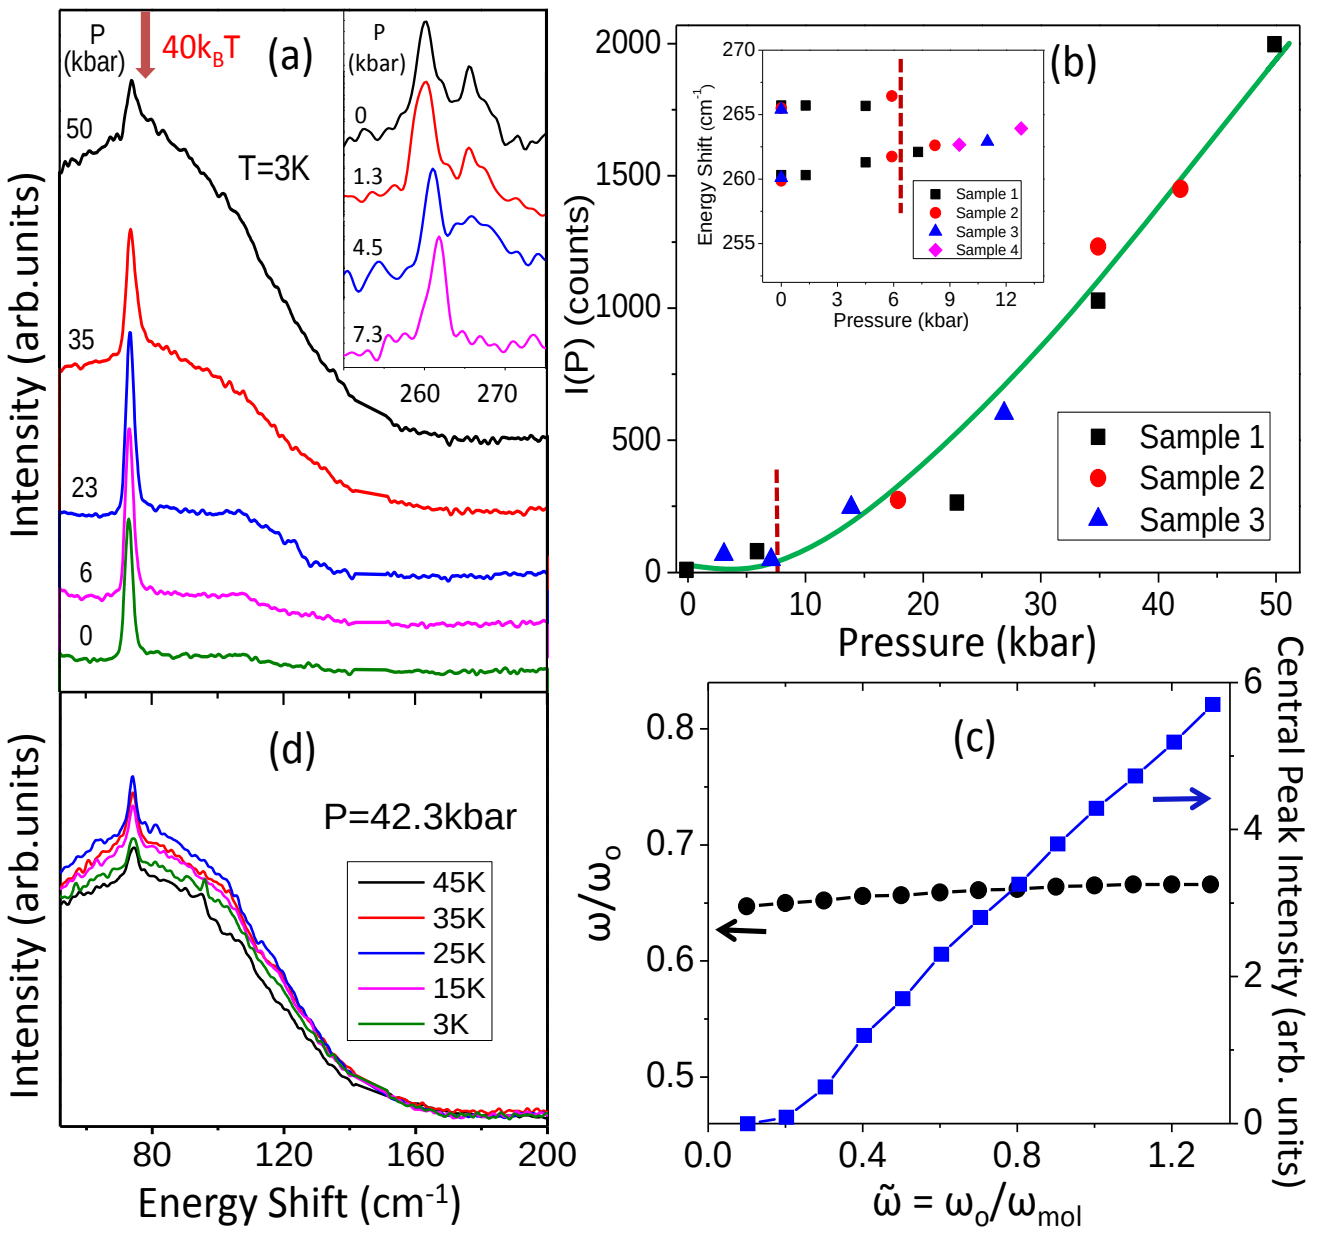

FIG. 2. (a) Pressure dependence of Raman spectra of $KCuF_3$ at $T = 3$ K. The arrow indicates a frequency corresponding to 40 k_BT. The inset illustrates the pressure dependence of the E_g phonon mode at $T = 3$ K. (b) Pressure dependence of the integrated central peak intensity, $I(P)$, at $T = 3$ K for three different samples of $KCuF_3$. The inset shows the pressure dependence of the peak energies of the E_g phonon mode at 3 K for four different samples, showing evidence for an orthorhombic-to-tetragonal transition near $P^* = 7$ kbar. (c) Calculated normalized phonon frequency, ω/ω_o, (black circles) and central peak integrated intensity (blue squares) as a function of ω_o/ω_{mol}, using Eq. 1 from [17]. (d) Temperature dependence of central peak response of $KCuF_3$ at $P = 42.3$ kbar.

ple relaxational response function $\chi''(\omega) \sim \frac{\omega\Gamma}{\omega^2+\Gamma^2}$,[26] which has a maximum value at the characteristic fluctuation rate Γ. Similar central peak responses have been observed to result from slow relaxational spin dynamics in magnetic materials (e.g., $UCu_{5-x}Pd_x$ [25], β-M_n [26]) and slow relaxational structural fluctuations in perovskites (e.g., $SrTiO_3$ [27], $LaAlO_3$ [28] and $KMnF_3$ [29]). In $KCuF_3$, we attribute the pressure-induced development of a quasielastic central peak to the onset of slow fluctuations of the CuF_6 octahedra with a characteristic fluctuation rate $\Gamma \sim 80$ cm^{-1} (10 meV). In support of this interpretation, Fig. 2 (c) shows that the phonon response function of Yamada *et al.* in Eq. 1 [17] predicts the development of a central peak — and the absence of phonon softening — when the molecular (i.e., CuF_6 octahedral) fluctuation rate (ω_{mol}) becomes comparable to the phonon frequency (ω_o).[17] The agreement between the pressure-induced development of a central peak in $KCuF_3$ (see Fig. 2 (a) and (b)) and the predictions of the Yamada model in the "slow molecular fluctuation regime" (see Fig. 2 (c)) suggests that pressure increases the molecular fluctuation rate relative to the phonon frequency (see Fig. 2(c)). It is worth noting also that a similar central peak neutron scattering response in isostructural $KMnF_3$ has also been attributed to dynamical rotations of the fluorine octahedra.[27]

These pressure results provide evidence for a pressure-tuned "quantum melting" transition near $T \sim 0$ in $KCuF_3$ between a static configuration of the CuF_6 octahedra to a phase in which the CuF_6 octahedra are slowly fluctuating on a timescale that is comparable to the E_g and B_{1g} phonon frequencies. Indeed several features of the pressure-induced central peak (fluctuational) response in $KCuF_3$ (Fig. 2) suggest that it is associated with quantum fluctuations of the CuF_6 octahedra: First, the characteristic energy scale of the fluctuations, $\Gamma \sim 80$ cm^{-1} (10 meV) is roughly 40 times the measured temperature ($T = 3$ K), i.e., $\Gamma \sim 40\ k_BT$ (see arrow in Fig. 2 (a)). Second, Fig. 2 (d) shows that the central peak scattering response of $KCuF_3$ at $P = 42$ kbar is temperature independent, which is expected for quantum fluctuations in the frequency regime of the observed central peak scattering, i.e., for $\hbar\omega \gg k_BT$.[23–25] A similar pressure-tuned quantum phase transition between ordered (ferroelectric) and fluctuating (quantum paraelectric) regimes was also observed in KH_2PO_4 (KDP).[30]

Altogether, these temperature- and pressure-dependent Raman results — summarized in Fig. 3 — suggest the following description of fluctuations in $KCuF_3$: Above $T = 50$ K and for $P = 0$, fast fluctuations ($\omega_{mol} \gg \omega_o$) of the CuF_6 octahedra result in soft-mode behavior associated with rotational F vibrations — as well as in other structural anomalies observed previously [11–14] — until a tetragonal-to-orthorhombic transition locks these fluctuations into a glassy configuration below $T = 50$ K (see Fig. 3).[16] Thus, the temperature dependent behavior of the structural fluctuations in $KCuF_3$ can be attributed to thermal fluctuations between different "wells" in a free energy landscape representing different octahedral configurations (top left diagram in Fig. 3); these configurations become locked into a static glassy configuration below $T = 50$ K, just prior to the Néel ordering temperature ($T_N \sim 40$ K). Above $P^* \sim 7$ kbar, however, the structural distortion that locks the octahedra into a static configuration is reversed, allowing slow fluctuations of the octahedra with $\omega_{mol} \leq \omega_o$; this leads to the development of a relaxational ("central peak") response associated with slow fluctuations between different octahedral configurations. Because the characteristic rate associated with these fluctuations is temperature independent [31] and more than an order-of-magnitude larger than the characteristic temperature, we propose that these fluctuations are primarily driven by zero-point fluctuations (i.e., quantum tunnelling) between different wells in the free energy landscape (top right diagram in Fig. 3). This interpretation suggests a pressure-induced "quantum

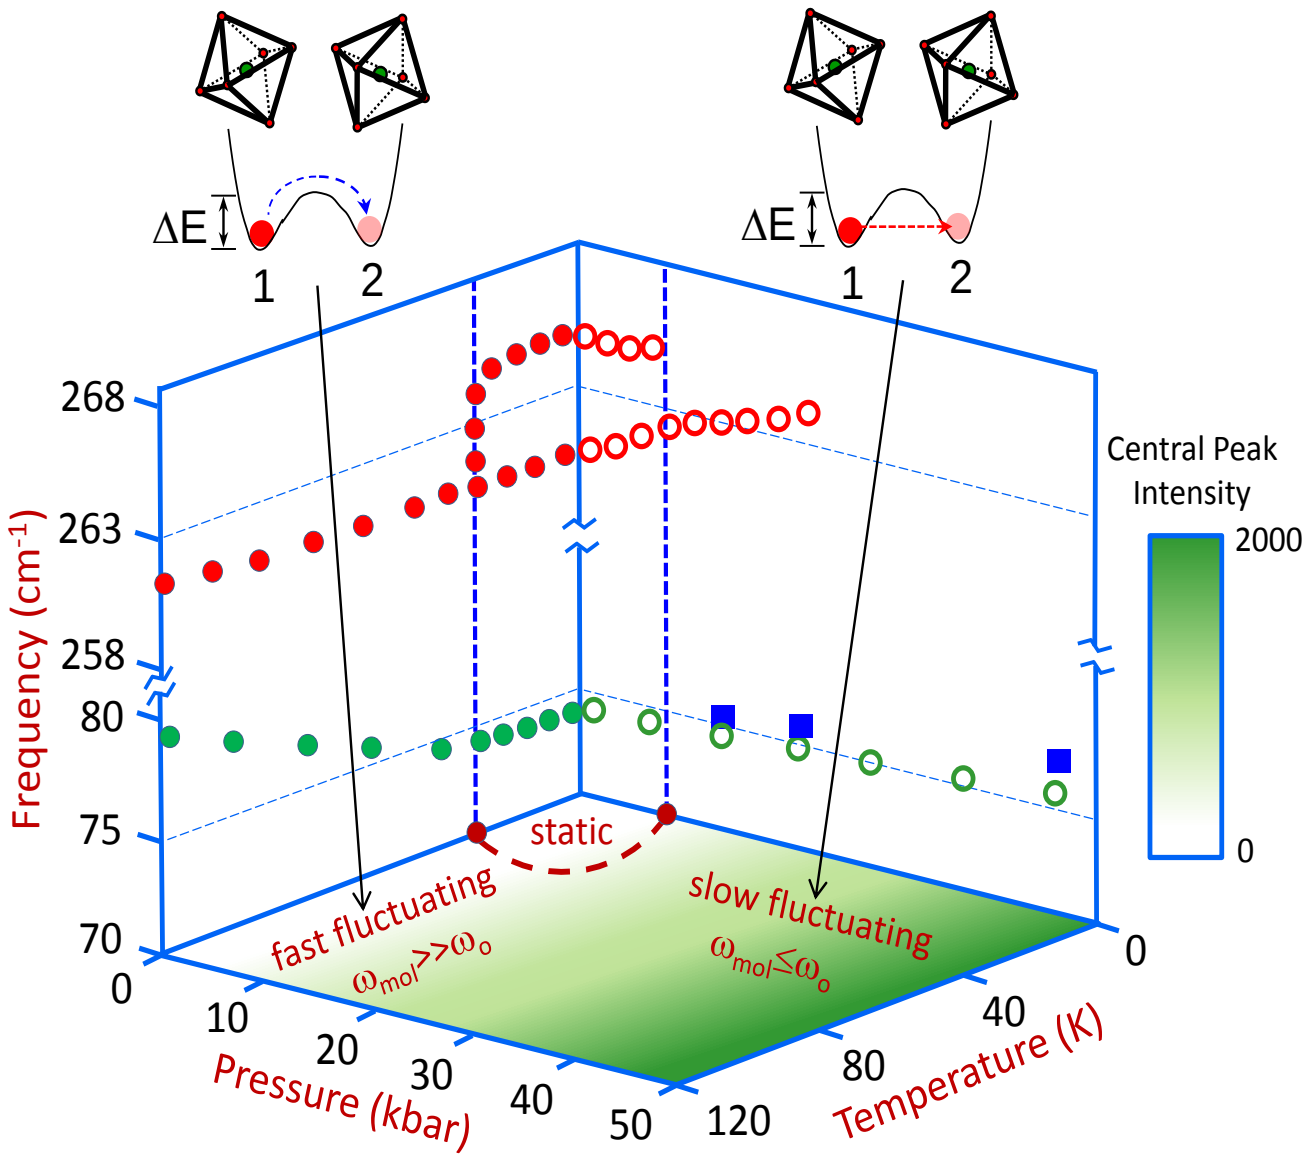

FIG. 3. *PT* phase diagram for the CuF_6 octahedral fluctuations in $KCuF_3$. Horizontal axes represent the temperature and pressure. The contour plot on the horizontal plane represents the measured fluctuational (central peak) integrated intensity, with dark green = 2000 counts and white = 0 counts, based on temperature sweeps at the following pressures: $P =$ 0, 5, 13, 18.7, 27, 35, 42 kbar. The vertical axis shows the mode frequency, with both the ~ 79 cm^{-1} B_{1g} and ~ 261 cm^{-1} E_g phonon frequencies shown as functions of temperature (filled red and green circles, respectively) and pressure (open red and green circles, respectively). Filled squares illustrate the characteristic energy Γ of the central peak response. Diagrams on top depict (left) thermally activated hopping between CuF_6 configurations in the fast-fluctuating regime of $KCuF_3$, and (right) the quantum tunneling between CuF_6 configurations in the pressure-tuned slow fluctuating regime.

melting" transition in $KCuF_3$ that is similar to "rotational melting" transitions [1] to quantum paraelectric phases in $SrTiO_3$ and $KTaO_3$ at low temperatures,[32] and in KDP at high pressures.[30]

One important question that remains to be answered concerns the role these octahedral fluctuations play in disrupting magnetic order in $KCuF_3$. A connection between quantum structural (octahedral) fluctuations and the spin and/or orbital degree of freedom might indicate that a pressure-induced orbital/spin liquid state accompanies quantum fluctuations of the octahedral orientations in $KCuF_3$. To study this important question, pressure dependent magnetic measurements are needed to test whether the pressure-tuned onset of octahedral fluctuations is coupled with a suppression of N*é*el order. Uniaxial pressure measurements would also provide an interesting comparison to these hydrostatic pressure studies,[1] by helping to stabilize the lower symmetry, static configuration of $KCuF_3$ and presumably extending the magnetic ground state.

This material is based on work supported by the U.S. Department of Energy, Division of Materials Sciences, under Award No. DE-FG02-07ER46453, through the Frederick Seitz Materials Research Laboratory at the University of Illinois at Urbana-Champaign, and by the National Science Foundation under Grant NSF DMR 08-56321. S. L. gratefully acknowledges financial support from the DST, Govt. of India through a Ramanujam Fellowship.

[1] E. Tosatti and R. Maronak, Sol. St. Commun. **92**, 167 (1994).
[2] L.F. Feiner, A.M. Oleś and J. Zaanen, Phys. Rev. Lett. **78**, 2799 (1997).
[3] B. Canals and C. Lacroix, Phys. Rev. Lett. **80**, 2933 (1998); S. Nakatsuji *et al.*, Phys. Rev. Lett. **96**, 087204 (2006); N.P. Ong and R.J. Cava, Science **305**, 52 (2004).
[4] K.I. Kugel and D.I. Khomskii, Sov. Phys.-Usp. **25**, 231 (1982).
[5] S.K. Satija *et al.*, Phys. Rev. B **21**, 2001 (1980).
[6] A. Okazaki and Y. Suemune, J. Phys. Soc. Jpn. **16**, 176 (1961).
[7] M.T. Hutchings *et al.*, Phys. Rev **188**, 919 (1969).
[8] B. Lake *et al.*, Nature Materials **4**, 329 (2005).
[9] L. Paolasini *et al.*, Phys. Rev. Lett. **88**, 106403 (2002).
[10] E. Pavarini, E. Koch and A.I. Lichtenstein, Phys. Rev. Lett. **101**, 266405 (2008).
[11] M. Hidaka, T. Eguchi and I. Yamada, J. Phys. Soc. Jpn. **67**, 2488 (1998).
[12] M.V. Eremin *et al.*, Phys. Rev. Lett. **101**, 147601 (2008).
[13] I. Yamada and N. Kato, J. Phys. Soc. Jpn. **63**, 289 (1994).
[14] C. Mazzoli *et al.*, J. Magn. Magn. Mater. **242**, 935 (2002).
[15] J. Deisenhofer *et al.*, Phys. Rev. Lett. **101**, 157406 (2008).
[16] J. C. T. Lee *et al.*, arXiv:0911.0619v1.
[17] Y. Yamada, H. Takatera and D.L. Huber, J. Phys. Soc. Jpn. **36**, 641 (1974).
[18] K. Hirakawa and Y. Kurogi, Suppl. Prog. Theor. Phys. **46**, 147 (1970).
[19] K. Hirakawa and H. Miike, Phys. Lett. **45A**, 79 (1973).
[20] T. Ueda *et al.*, Sol. St. Commun. **80**, 801 (1991).
[21] M. Hücker *et al.*, Phys. Rev. Lett. **104**, 057004 (2010).
[22] P. Steffens *et al.*, Phys. Rev. B **72**, 094104 (2005).
[23] C. S. Snow *et al.*, Phys. Rev. Lett. **89**, 226401 (2002).
[24] I. Loa *et al.*, Phys. Rev. Lett. **87**, 125501 (2001).
[25] M.C. Aronson *et al.*, Phys. Rev. Lett. **75**, 725 (1995).
[26] H. Nakamura *et al.*, J. Phys.: Condens. Matter **9**, 4701 (1997).
[27] S.M. Shapiro *et al.*, Phys. Rev. B **6**, 4332 (1972).
[28] J.K. Kjems *et al.*, Phys. Rev. B **8**, 1119 (1973).
[29] K. Gesi, J.D. Axe and G. Shirane, Phys. Rev. B **5**, 1933 (1972).
[30] G.A. Samara, Phys. Rev. Lett. **27**, 103 (1971).
[31] O.G. Shpyrko *et al.*, Nature **447**, 68 (2007).
[32] D. Merunka and B. Rakvin, Struct. Bond. **124**, 149 (2007).